



Impact of classical statistics on thermal conductivity predictions of BAs and diamond using machine learning molecular dynamics

October 2024

Changing the World's Energy Future

Hao Zhou, Tianli Feng, Shuxiang Zhou, Zilong Hua, Kaustubh Krishna Bawane



INL is a U.S. Department of Energy National Laboratory operated by Battelle Energy Alliance, LLC

DISCLAIMER

This information was prepared as an account of work sponsored by an agency of the U.S. Government. Neither the U.S. Government nor any agency thereof, nor any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness, of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. References herein to any specific commercial product, process, or service by trade name, trade mark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the U.S. Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the U.S. Government or any agency thereof.

Impact of classical statistics on thermal conductivity predictions of BAs and diamond using machine learning molecular dynamics

Hao Zhou, Tianli Feng, Shuxiang Zhou, Zilong Hua, Kaustubh Krishna Bawane

October 2024

**Idaho National Laboratory
Idaho Falls, Idaho 83415**

<http://www.inl.gov>

**Prepared for the
U.S. Department of Energy
Under DOE Idaho Operations Office
Contract DE-AC07-05ID14517**

Impact of classical statistics on thermal conductivity predictions of BAs and diamond using machine learning molecular dynamics

Hao Zhou¹, Shuxiang Zhou², Zilong Hua², Kaustubh Bawane², Tianli Feng^{1*}

¹Department of Mechanical Engineering, University of Utah, Salt Lake City, Utah 84112, USA

²Idaho National Laboratory, Idaho Falls, Idaho 83415, USA

Corresponding Authors

*Email: tianli.feng@utah.edu

Abstract

Machine learning interatomic potentials (MLIPs) have greatly enhanced molecular dynamics (MD) simulations, achieving near-first-principles accuracy in thermal conductivity studies. In this work, we reveal that this accuracy, observed in BAs and diamond at sub-Debye temperatures, stems from an accidental error-cancellation: classical statistics overestimates specific heat while underestimating phonon lifetimes, balancing out in thermal conductivity predictions. However, this balance is disrupted when isotopes are introduced, leading MLIP-based MD to significantly underpredict thermal conductivity compared to experiments and quantum statistics-based Boltzmann transport equation (BTE). This discrepancy arises not from classical statistics affecting phonon-isotope scattering rates, but from its impact on the interplay between phonon-isotope and phonon-phonon scattering, in the Normal scattering-dominated BAs and diamond. This work underscores the limitations of MLIP-based MD for thermal conductivity studies at sub-Debye temperatures.

Keywords: Thermal Conductivity, Machine Learning Interatomic Potentials, Molecular Dynamics, Phonon Statistics, Isotope

The emergence of machine learning interatomic potentials (MLIPs) has significantly advanced molecular dynamics (MD) simulations^{1,2}. By leveraging first-principles calculations as input, MLIPs are able to describe the interatomic interactions at a near-first-principles accuracy. This accuracy extends from the second-order to the third and even fourth-order force constants³. Naturally, MLIP-based MD (MLMD) has emerged as a powerful method to simulate thermal transport in materials, achieving significantly higher accuracy in thermal conductivity prediction than empirical interatomic potentials⁴. For materials that are challenging to fit with empirical interatomic potentials, MLIPs are even more indispensable.

Surprisingly, it has been extensively shown that MLMD can predict the thermal conductivity accurately even at sub-Debye temperatures, when the classical statistics in MD deviate significantly from quantum statistics. For instance, for Si⁵, β -Ga₂O₃⁶, cubic BAs⁷, and diamond⁷, which have Debye temperatures of around 635⁸, 870⁹, 680¹⁰, and 2240 K¹¹, respectively, the thermal conductivities predicted by MLMD using different MLIPs all closely match the experimental data at 300 K. Therefore, some work even suggested that quantum correction (QC) is unnecessary for predicting the thermal conductivities when using MLIPs^{6,7}. However, this claim lacks a solid foundation. The role of classical statistics in MLMD for predicting thermal conductivity at sub-Debye temperatures remains unclear.

In this Letter, we investigate the impact of statistics on thermal conductivity predictions in MLMD. BAs and diamond are selected for study for three reasons. 1) As the first and second highest-thermal conductivity materials in nature, BAs and diamond hold great potential for next-generation electronics. 2) BAs and diamond have been extensively studied in the literature by using both DFT and MD, providing ample data for comparison. 3) With high Debye temperatures, BAs and diamond are ideal candidates for studying the effects of classical statistics at sub-Debye temperatures. Here, both pure and isotope-contained BAs and diamond are studied. The moment tensor potential (MTP)¹² is selected owing to its efficiency, reliability, and simplicity. Green-Kubo theory^{13,14} is used to extract the thermal conductivity of materials based on the autocorrelation function of heat current from MD simulations. Phonon spectral energy density (SED)¹⁵ analysis is performed based on MD trajectories to extract phonon scattering rates. For reference, Boltzmann transport equation (BTE) calculations are performed with three- and four-phonon (3ph, 4ph) scattering rates obtained from density functional theory (DFT). Phonon-isotope scattering is calculated by using the Tamura formula based on Fermi's Gold rule. All the simulation details can be found in the Supplemental materials¹⁶ and our previous work¹⁷.

MTPs are trained for isotope-free and isotope-mixed BAs and diamond. The accuracy of MTPs is demonstrated by comparing the predicted forces and energies with DFT calculations as shown in Fig. 1 and Fig. S1-S2¹⁶. The root mean square error (RMSE) of energies and forces for BAs are 0.144 meV/atom and 0.017 eV/Å, respectively, and 0.060 meV/atom and 0.010 eV/Å for diamond, respectively. The phonon dispersions calculated using MTP and DFT agree with each other, as shown in Fig. 1(c,f), demonstrating the accuracy of MTPs.

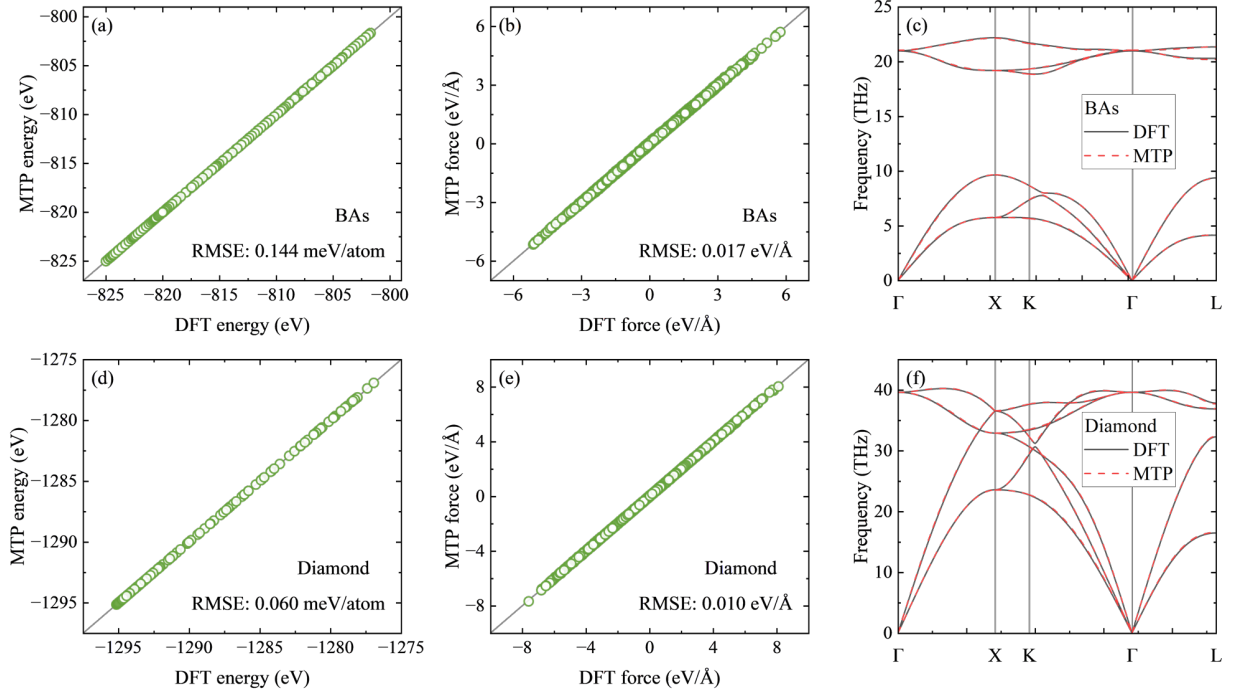


FIG. 1. Comparison between MTP for (a-c) BAs and (d-f) diamond. (a,d) Energies. (b,e) Interatomic forces. (e,f) Phonon dispersion.

The thermal conductivities of BAs and diamond calculated using MLMD are shown in Fig. 2. Without isotopes, the temperature-dependent thermal conductivities of both materials agree well with those calculated from DFT, being consistent with the literature⁷. However, when isotopes are present, while the DFT calculations agree excellently with experiment^{18–24}, MLMD significantly underpredicts the thermal conductivity of both materials. For example, for isotopically pure BAs, DFT and MLMD yield 1500 and 1300 W/mK, respectively, closely matching experimental data (1500 W/mK)²¹. For isotopically pure diamond, DFT and MLMD yield 3500 and 3400 W/mK, also aligning with experimental data (3300 W/mK)^{22–24}. However, for natural BAs, the MLMD result (760 W/mK) is significantly lower than both DFT (1300 W/mK) and experimental data

(1300 W/mK). Similarly, for natural diamond, the MLMD result (1500 W/mK) is much lower than DFT (2300 W/mK) and experimental data (2400 W/mK).

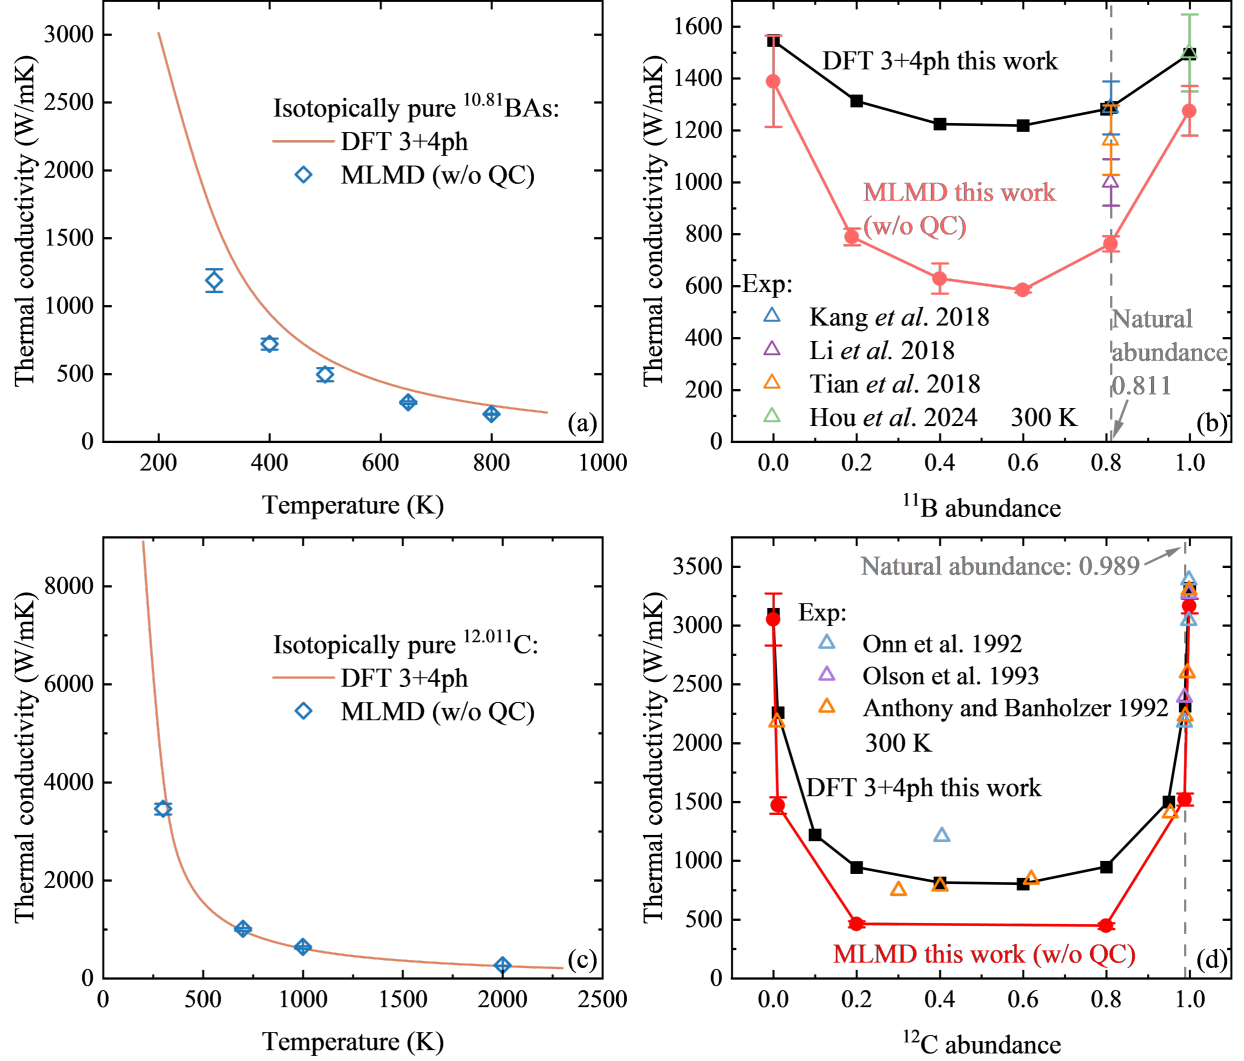


FIG. 2. Thermal conductivity of (a) isotope-free BAs, (b) isotope-mixed BAs, (c) isotope-free diamond, and (d) isotope-mixed diamond. References of experimental data in (b): Kang et al. 2018²⁰, Li et al. 2018¹⁸, Tian et al. 2018¹⁹, Hou et al. 2024²¹, and in (c): Anthony and Banholzer 1992²², Onn et al. 1992²³, and Olson et al. 1993²⁴.

To investigate why MLMD predicts thermal conductivities well without isotopes but inaccurately with isotopes, we look into phonon specific heat and lifetime. Figures 3(a,d) show $\kappa_{\text{MLMD}}/\kappa_{\text{DFT}}$, $c_{\text{MLMD}}/c_{\text{DFT}}$, and $\tau_{\text{MLMD}}/\tau_{\text{DFT}}$ for isotopically pure BAs and diamond, respectively, where κ is thermal conductivity, c is specific heat, and τ is phonon lifetime. Here, $\tau_{\text{MLMD}}/\tau_{\text{DFT}}$ is indirectly obtained by using $\tau_{\text{MLMD}}/\tau_{\text{DFT}} = \kappa_{\text{MLMD}}/\kappa_{\text{DFT}} \cdot c_{\text{DFT}}/c_{\text{MLMD}}$. It is seen that MLMD overestimates specific heat and underestimates phonon lifetimes significantly, especially at low temperatures. These two errors accidentally cancel each other out, resulting in an apparently accurate thermal conductivity prediction. The errors gradually shrink and disappear as temperature increases.

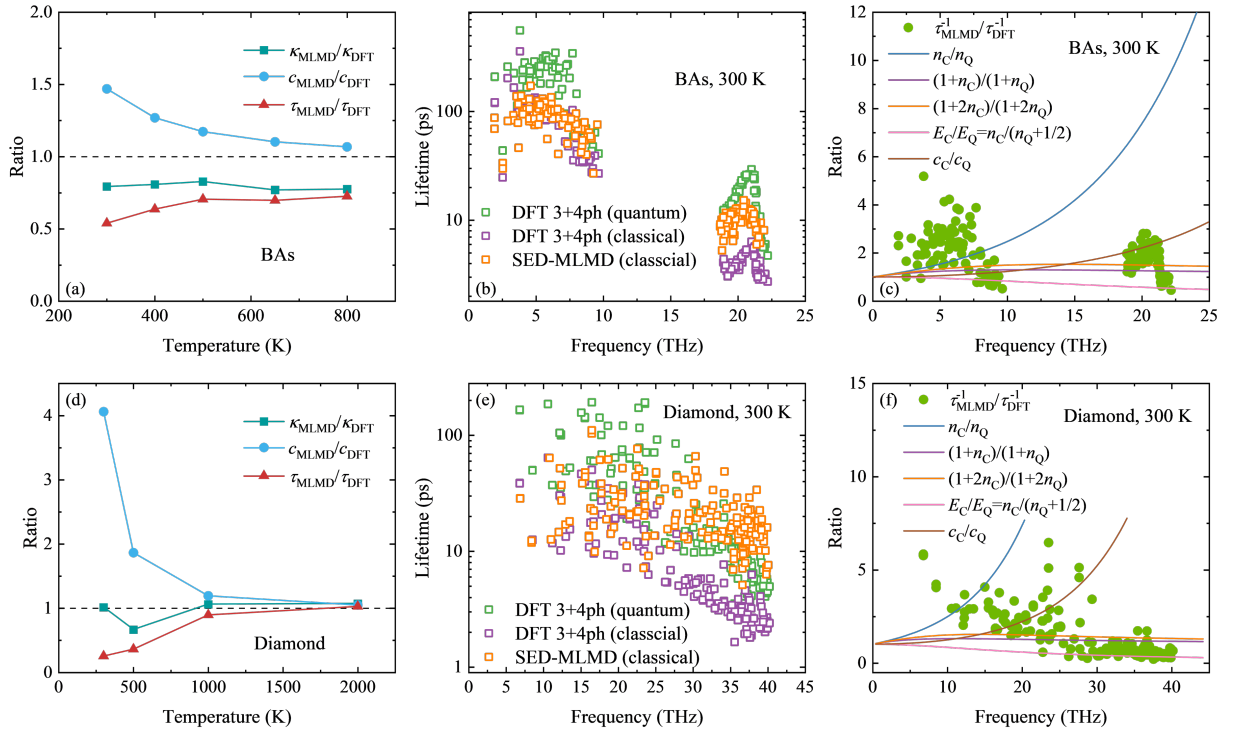


FIG. 3. Comparison between quantum and classical statistics-predicted thermal properties of (a-c) BAs and (b-d) diamond. (a,d) Ratios of thermal conductivity, total specific heat, and effective phonon lifetime obtained from MD and DFT as a function of temperature. (b,e) Mode-level

phonon scattering rates at room temperature. (c,f) Possible quantum corrections for mode-level phonon scattering rates.

In addition to the phonon lifetime ratio ($\tau_{\text{MLMD}}/\tau_{\text{DFT}}$) that is derived indirectly from thermal conductivity and specific heat, the mode-dependent τ_{MLMD} and τ_{DFT} are directly extracted and compared with each other, as shown in Figs. 3(b,e). Indeed, MLMD significantly underestimates the lifetime compared to DFT, supporting the error-cancellation claim and the observation in Figs. 3(a,d). Furthermore, it is seen that the phonon lifetime underestimation in MLMD is more prominent for lower frequency phonons. This is surprising since classical statistics deviate from quantum statistics relatively smaller for lower frequency phonons than for higher-frequency phonons. We hypothesize that these lower-frequency phonons, despite having smaller statistics-induced errors, may scatter significantly with higher-frequency phonons, which have larger statistics-induced errors. This can also be seen by replacing the quantum phonon population (n_{Q}) in the 3,4-phonon scattering formalism with the classical population (n_{C}), as shown in Figs. 3(b,e). But it is noted that replacing n_{Q} with n_{C} in phonon scattering formalism is not a scientific way to obtain phonon lifetime under classical statistics. This is because the phonon scattering formalism is derived based on n_{Q} . Without n_{Q} , the phonon scattering formalism is not valid anymore^{25–29}. Actually, since n_{C} is larger than n_{Q} by 0.5 at the classical limit, replacing n_{Q} with $n_{\text{C}} - 0.5$ in the phonon scattering formalism can yield better thermal conductivity than using n_{C} (see Fig. S3¹⁶).

To eliminate the errors caused by classical statistics, quantum corrections, if possible, need to be done on both specific heat and phonon scattering rate. The discussion of quantum corrections has a long history. In early years, QC was done by correcting the temperature, via equating the total

energies of classical and quantum systems^{30–32}, i.e., $\sum E_C n_C = \sum E_Q n_Q$. While many early studies used this QC method, it was demonstrated to be unreasonable by Turney and McGaughey in 2009²⁶ no matter the zero-point energy is considered or not. They used anharmonic lattice dynamics with Stillinger-Weber potential to self-consistently demonstrate this by replacing the n_Q with $n_C - 1/2$. They also found that both specific heat and lifetime were affected by the statistics, and thus QC should be performed on both. In addition, QC should be applied on a mode level instead of a system level. Despite the discovery of Turney and McGaughey, QC has been primarily applied to specific heat only^{33–38}. On the one hand, QC to lifetime is difficult and remains unfeasible, while that to specific heat is simple. On the other hand, it is found that the QC to lifetime is only important for crystalline materials^{25,33,34,39}. QC to specific heat is sufficient for strongly disordered systems where phonon-phonon scattering is not dominant. Gu et al.²⁵ also mentioned in their review paper that QC should be applied to both specific heat and lifetime for crystals, but these two factors often cancel out each other, making the overall impact not strong, such as in graphene and silicon. However, the two factors were not cancelled out in the 1-D material, carbon nanotubes, as studied by Barbalinardo et al.³⁹. They limit \hbar to zero to approach classical limit in solving the BTE, and a large gap is found between the thermal conductivity obtained using n_Q and n_C . Puligheddu et al.²⁷ found, using classical potentials, that the phonon lifetimes of MgO and PbTe obtained by replacing n_Q with n_C in BTE agree well with those obtained from MD with SED analysis, ending with the conclusion that phonon lifetime can be corrected by correcting the phonon population. This finding does not hold in the systems studied in this work (i.e., BAs and diamond), where we find that replacing n_Q with n_C in BTE results in unphysical results that cannot match with MD. In light of these efforts, here we explore several possible quantum correction methods for mode-level phonon lifetime, shown in Figs. 3(c,f). Based on the three-phonon scattering formalism, phonon scattering

rate is generally proportional to phonon population at high temperatures. Therefore, the first trial to correct τ is to use n_C/n_Q , which, however, is found to not match with $\tau_{\text{MLMD}}^{-1}/\tau_{\text{DFT}}^{-1}$. Considering the three-phonon scattering contains $(1+n)$ and $(1+2n)$ terms, the second trial is to use $(1+n_C)/(1+n_Q)$ and $(1+2n_C)/(1+2n_Q)$ for corrections, which are found to not match with $\tau_{\text{MLMD}}^{-1}/\tau_{\text{DFT}}^{-1}$ either. Other trials, like using E_C/E_Q and c_C/c_Q , all fail. It is found that τ is overpredicted by classical statistics more for lower frequency phonons, but all these corrections correct less lower frequency phonons. These indicate that the quantum correction to phonon-phonon scattering rate is complex and is unlikely to be achieved in a straightforward manner.

After understanding the isotope-free materials, we explore the reasons for the significant underestimation of thermal conductivity by MLMD when isotopes are present. Theoretically, the phonon-isotope scattering rate ($\tau_{\text{ph-iso}}^{-1}$) should not depend on phonon population, based on the derivation of Tamura's formula using perturbation theory⁴⁰. Numerically, this is verified by comparing the $\tau_{\text{ph-iso}}^{-1}$ calculated by Tamura's formula ($\tau_{\text{ph-iso}}^{-1} = \pi/2 \cdot \omega^2 g \cdot \text{pDOS}$) and $\tau_{\text{ph-iso}}^{-1} = \tau_{\text{tot}}^{-1} - \tau_{\text{ph-ph}}^{-1}$ obtained by SED analysis of MLMD, where ω is phonon frequency, g factor is determined by isotope mass and concentration, pDOS is projected density of state, and τ_{tot}^{-1} and $\tau_{\text{ph-ph}}^{-1}$ are the phonon linewidths in isotope-contained and isotope-free materials, respectively. As seen in Fig. 4(a,b), $\tau_{\text{ph-iso}}^{-1}$ obtained from the two methods agree with each other, supporting that $\tau_{\text{ph-iso}}^{-1}$ does not depend on phonon statistics. We note that some negative $\tau_{\text{ph-iso}}^{-1}$ data obtained by $\tau_{\text{ph-iso}}^{-1} = \tau_{\text{tot}}^{-1} - \tau_{\text{ph-ph}}^{-1}$ are due to the large uncertainty of SED analysis, especially when τ_{tot}^{-1} and $\tau_{\text{ph-ph}}^{-1}$ are very close. The $\tau_{\text{ph-iso}}^{-1}$ obtained by Tamura's formula using classical and quantum statistics also agree with each other for an artificial isotope abundance of

BAs as shown in Fig. 4(c). Another evidence is temperature dependence. It is found that $\tau_{\text{ph-iso}}^{-1}$ does not depend on temperature in MLMD, indicating that $\tau_{\text{ph-iso}}^{-1}$ is invariant on phonon population.

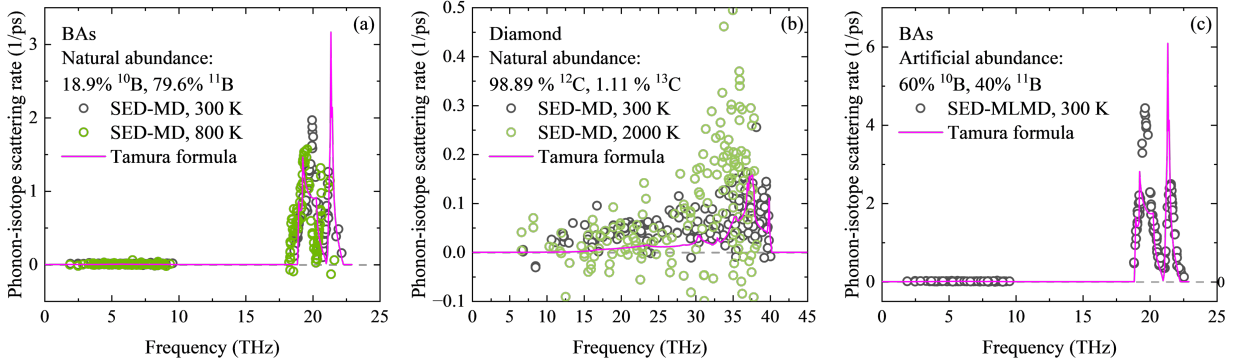


FIG. 4. Phonon-isotope scattering rates obtained from SED based on MD and Tamura formula for natural abundant (a) BAs and (b) diamond, and (c) BAs with artificial isotope abundance.

Since τ_{ph}^{-1} is larger in MLMD than DFT, adding the same $\tau_{\text{ph-iso}}^{-1}$ is expected to generate smaller impact in MLMD, resulting in larger thermal conductivity in MLMD than DFT. However, the fact is that MLMD shows smaller thermal conductivity than DFT for isotope-contained materials. A possible reason is that the isotopes do not only introduce phonon-isotope scattering but also change the original phonon-phonon scattering. This can be realized by the hydrodynamical behavior of phonons in BAs and diamond. In these two materials, the moment-conserved Normal scattering dominates over the moment-unconserved Umklapp scattering, resulting in hydrodynamical movement of phonons^{28,41}. Therefore, the single-mode relaxation time approximation (SMRTA) fails in describing thermal transport in BAs and diamond. The exact solution of BTE using iteration shows much higher thermal conductivity than SMRTA. Even though phonon statistics do not change $\tau_{\text{ph-iso}}^{-1}$ in SMRTA, it changes how Normal scattering is coupled with Umklapp scattering

in the iteration in solving BTE. As seen in Fig. 5, using classical statistics gives a much smaller increase of thermal conductivity after iteration than using quantum statistics. This is understandable since isotope scattering is preferable for high energy phonons and gives positive feedback to Umklapp scattering and increases the resistance. Consequently, the role of statistics becomes more complicated when a material is dominated by Normal scattering processes.

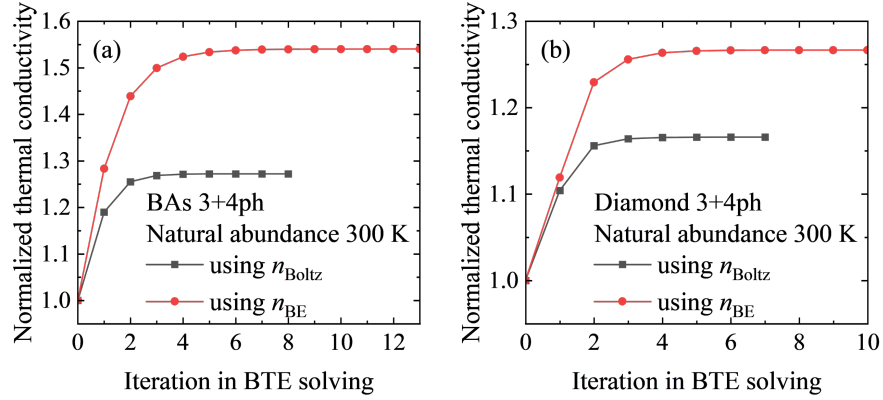


FIG. 5. Normalized thermal conductivity of isotopically mixed (a) BAs and (b) diamond with natural abundance obtained in ShengBTE at 300 K as a function of iteration step.

In conclusion, we investigate the effects of phonon statistics on the thermal conductivity prediction of BAs and diamond using MLMD. We find that while MLMD, without any quantum correction, can well reproduce the thermal conductivity of isotopically pure BAs and diamond, it is an error-canceling effect: the classical statistics in MLMD overestimates specific heat and underestimates phonon lifetime. This error-canceling effect is disrupted when isotopes are introduced, leading MLMD to significantly underpredict thermal conductivity compared to experiments and quantum statistics-based BTE. This discrepancy is not because classical statistics changes phonon-isotope scattering rates, but because the isotopes changes phonon-phonon scattering mechanisms.

Additionally, our results support the validity of the Tamura formula for phonon-isotope scattering. We hope this study provides a deeper understanding of thermal conductivity in MLMD simulations.

References

- ¹ B. Mortazavi, X. Zhuang, T. Rabczuk, and A. V. Shapeev, “Atomistic modeling of the mechanical properties: the rise of machine learning interatomic potentials,” *Mater Horiz* **10**(6), 1956–1968 (2023).
- ² Y. Luo, M. Li, H. Yuan, H. Liu, and Y. Fang, “Predicting lattice thermal conductivity via machine learning: a mini review,” *NPJ Comput Mater* **9**(1), 4 (2023).
- ³ Z. Liu, X. Yang, B. Zhang, and W. Li, “High thermal conductivity of wurtzite boron arsenide predicted by including four-phonon scattering with machine learning potential,” *ACS Appl Mater Interfaces* **13**(45), 53409–53415 (2021).
- ⁴ X. Qian, and R. Yang, “Machine learning for predicting thermal transport properties of solids,” *Materials Science and Engineering R: Reports* **146**(September), 100642 (2021).
- ⁵ X. Qian, S. Peng, X. Li, Y. Wei, and R. Yang, “Thermal conductivity modeling using machine learning potentials: application to crystalline and amorphous silicon,” *Materials Today Physics* **10**, (2019).
- ⁶ R. Li, Z. Liu, A. Rohskopf, K. Gordiz, A. Henry, E. Lee, and T. Luo, “A deep neural network interatomic potential for studying thermal conductivity of β -Ga₂O₃,” *Appl Phys Lett* **117**(15), (2020).
- ⁷ Y. Ouyang, C. Yu, J. He, P. Jiang, W. Ren, and J. Chen, “Accurate description of high-order phonon anharmonicity and lattice thermal conductivity from molecular dynamics simulations with machine learning potential,” *Phys Rev B* **105**(11), 1–10 (2022).
- ⁸ P.H. Keesom, and G. Seidel, “Specific Heat of Germanium and Silicon at Low Temperatures,” *Physical Review* **113**(1), 33–39 (1959).
- ⁹ H. He, M.A. Blanco, and R. Pandey, “Electronic and thermodynamic properties of β -Ga₂O₃,” *Appl Phys Lett* **88**(26), 2–5 (2006).
- ¹⁰ K. Yaddanapudi, “Ab initio calculations of the thermal properties of boron arsenide,” *Comput Mater Sci* **184**(June), 109887 (2020).
- ¹¹ T. Tohei, A. Kuwabara, F. Oba, and I. Tanaka, “Debye temperature and stiffness of carbon and boron nitride polymorphs from first principles calculations,” *Phys Rev B* **73**(6), 064304 (2006).
- ¹² A. V. Shapeev, “Moment Tensor Potentials: A Class of Systematically Improvable Interatomic Potentials,” *Multiscale Modeling & Simulation* **14**(3), 1153–1173 (2016).
- ¹³ M.S. Green, “Markoff Random Processes and the Statistical Mechanics of Time-Dependent Phenomena. II. Irreversible Processes in Fluids,” *J Chem Phys* **22**(3), 398–413 (1954).

- ¹⁴ R. Kubo, “Statistical-Mechanical Theory of Irreversible Processes. I. General Theory and Simple Applications to Magnetic and Conduction Problems,” J Physical Soc Japan **12**(6), 570–586 (1957).
- ¹⁵ J.A. Thomas, J.E. Turney, R.M. Iutzi, C.H. Amon, and A.J.H. McGaughey, “Predicting phonon dispersion relations and lifetimes from the spectral energy density,” Phys Rev B Condens Matter Mater Phys **81**(8), 1–4 (2010).
- ¹⁶ “Suppl holder,” (n.d.).
- ¹⁷ H. Zhou, J. Tiwari, and T. Feng, “Understanding the flat thermal conductivity of LaZr_2O_7 at,” Phys Rev Mater **8**(4), 043804 (2024).
- ¹⁸ S. Li, Q. Zheng, Y. Lv, X. Liu, X. Wang, P.Y. Huang, D.G. Cahill, and B. Lv, “High thermal conductivity in cubic boron arsenide crystals,” Science (1979) **361**(6402), 579–581 (2018).
- ¹⁹ F. Tian, B. Song, X. Chen, N.K. Ravichandran, Y. Lv, K. Chen, S. Sullivan, J. Kim, Y. Zhou, T.H. Liu, M. Goni, Z. Ding, J. Sun, G.A.G.U. Gamage, H. Sun, H. Ziyadee, S. Huyan, L. Deng, J. Zhou, A.J. Schmidt, S. Chen, C.W. Chu, P.Y. Huang, D. Broido, L. Shi, G. Chen, and Z. Ren, “Unusual high thermal conductivity in boron arsenide bulk crystals,” Science (1979) **361**(6402), 582–585 (2018).
- ²⁰ J.S. Kang, M. Li, H. Wu, H. Nguyen, and Y. Hu, “Experimental observation of high thermal conductivity in boron arsenide,” Science (1979) **361**(6402), 575–578 (2018).
- ²¹ S. Hou, F. Pan, X. Shi, Z.E. Nataj, F. Kargar, and ..., “Ultrahigh Thermal Conductivity of Cubic Boron Arsenide with an Unexpectedly Strong Temperature Dependence,” ArXiv Preprint ArXiv ..., 1–14 (2024).
- ²² T.R. Anthony, and W.F. Banholzer, “Properties of diamond with varying isotopic composition,” Diam Relat Mater **1**(5–6), 717–726 (1992).
- ²³ D.G. Onn, A. Witek, Y.Z. Qiu, T.R. Anthony, and W.F. Banholzer, “Some aspects of the thermal conductivity of isotopically enriched diamond single crystals,” Phys Rev Lett **68**(18), 2806–2809 (1992).
- ²⁴ J.R. Olson, R.O. Pohl, J.W. Vandersande, A. Zoltan, T.R. Anthony, and W.F. Banholzer, “Thermal conductivity of diamond between 170 and 1200 K and the isotope effect,” Phys Rev B **47**(22), 14850–14856 (1993).
- ²⁵ X. Gu, Z. Fan, and H. Bao, “Thermal conductivity prediction by atomistic simulation methods: Recent advances and detailed comparison,” J Appl Phys **130**(21), (2021).
- ²⁶ J.E. Turney, A.J.H. McGaughey, and C.H. Amon, “Assessing the applicability of quantum corrections to classical thermal conductivity predictions,” Phys Rev B **79**(22), 224305 (2009).
- ²⁷ M. Puligheddu, Y. Xia, M. Chan, and G. Galli, “Computational prediction of lattice thermal conductivity: A comparison of molecular dynamics and Boltzmann transport approaches,” Phys Rev Mater **3**(8), 085401 (2019).
- ²⁸ T. Feng, and X. Ruan, “Quantum mechanical prediction of four-phonon scattering rates and reduced thermal conductivity of solids,” Phys Rev B **93**(4), 045202 (2016).

- ²⁹ T. Feng, and X. Ruan, “Prediction of Spectral Phonon Mean Free Path and Thermal Conductivity with Applications to Thermoelectrics and Thermal Management: A Review,” *J Nanomater* **2014**, 1–25 (2014).
- ³⁰ C.Z. Wang, C.T. Chan, and K.M. Ho, “Tight-binding molecular-dynamics study of phonon anharmonic effects in silicon and diamond,” *Phys Rev B* **42**(17), 11276–11283 (1990).
- ³¹ Y.H. Lee, R. Biswas, C.M. Soukoulis, C.Z. Wang, C.T. Chan, and K.M. Ho, “Molecular-dynamics simulation of thermal conductivity in amorphous silicon,” *Phys Rev B* **43**(8), 6573–6580 (1991).
- ³² T. Feng, B. Qiu, and X. Ruan, “Anharmonicity and necessity of phonon eigenvectors in the phonon normal mode analysis,” *J Appl Phys* **117**(19), (2015).
- ³³ Y. Wang, Z. Fan, P. Qian, M.A. Caro, and T. Ala-Nissila, “Quantum-corrected thickness-dependent thermal conductivity in amorphous silicon predicted by machine learning molecular dynamics simulations,” *Phys Rev B* **107**(5), 054303 (2023).
- ³⁴ W. Lv, and A. Henry, “Direct calculation of modal contributions to thermal conductivity via Green–Kubo modal analysis,” *New J Phys* **18**(1), 013028 (2016).
- ³⁵ K. Sääskilahti, J. Oksanen, J. Tulkki, A.J.H. McGaughey, and S. Volz, “Vibrational mean free paths and thermal conductivity of amorphous silicon from non-equilibrium molecular dynamics simulations,” *AIP Adv* **6**(12), (2016).
- ³⁶ W. Sha, X. Dai, S. Chen, B. Yin, and F. Guo, “Phonon thermal transport in two-dimensional PbTe monolayers via extensive molecular dynamics simulations with a neuroevolution potential,” *Materials Today Physics* **34**(January), 101066 (2023).
- ³⁷ K. Xu, Y. Hao, T. Liang, P. Ying, J. Xu, J. Wu, and Z. Fan, “Accurate prediction of heat conductivity of water by a neuroevolution potential,” *Journal of Chemical Physics* **158**(20), (2023).
- ³⁸ Y. Zhou, “Assessing the quantum effect in classical thermal conductivity of amorphous silicon,” *J Appl Phys* **129**(23), (2021).
- ³⁹ G. Barbalinardo, Z. Chen, H. Dong, Z. Fan, and D. Donadio, “Ultrahigh Convergent Thermal Conductivity of Carbon Nanotubes from Comprehensive Atomistic Modeling,” *Phys Rev Lett* **127**(2), 025902 (2021).
- ⁴⁰ S.-I. Tamura, “Isotope scattering of dispersive phonons in Ge,” *Phys Rev B* **27**(2), 858–866 (1983).
- ⁴¹ T. Feng, L. Lindsay, and X. Ruan, “Four-phonon scattering significantly reduces intrinsic thermal conductivity of solids,” *Phys Rev B* **96**(16), 1–6 (2017).

Data availability

Source data are provided with this paper. All other data that support the plots within this paper are available from the corresponding authors on reasonable request.

Code availability

The codes used in this study are available from the corresponding authors upon request.

Acknowledgments

This work is supported by the INL Laboratory Directed Research and Development (LDRD) Program under DOE Idaho Operations Office Contract DE-AC07-05ID14517, LDRD Project ID 23A1070-064FP. H.Z. and T.F. also acknowledge the support from the National Science Foundation (NSF) (Award No. CBET 2212830). The computation used Center for High Performance Computing (CHPC) at the University of Utah, Bridges-2 at Pittsburgh Supercomputing Center through allocation PHY220002 from the Advanced Cyberinfrastructure Coordination Ecosystem: Services & Support (ACCESS) program, which is supported by NSF grants #2138259, #2138286, #2138307, #2137603, and #2138296, and Idaho National Laboratory's High Performance Computing systems located at the Collaborative Computing Center and supported by the Office of Nuclear Energy of the U.S. Department of Energy and the Nuclear Science User Facilities under Contract No. DE-AC07-05ID14517.

Competing interests

The authors declare no competing interests.

Additional information

Correspondence and requests for materials should be addressed to T.F.